

# THE EFFECT OF PROPYLENE GLYCOL CONCENTRATION ON THE PHYSICAL CHARACTERISTIC AND RELEASE RATE OF CAFFEINE IN GEL

Endang Diyah Ikasari, Milani

Sekolah Tinggi Ilmu Farmasi “Yayasan Pharmasi” Semarang

## Abstract

*The aims of this research were to find if any the effects of the propylene glycol concentration on the physical characteristics of the gel which includes organoleptic, pH, viscosity, and of the caffeine releasing test within 360' that includes the value of dissolution-%, DE-%, lag time, and diffusion coefficient.*

*Caffeine gel formulation consisted of F I (with 10% of propylene glycol addition), F II (with 20% of propylene glycol addition), F III (with 30% of propylene glycol addition), IV (without of propylene glycol addition) and the F V used as a positive control, an anti cellulite gel preparation that was available in the market used. Based on physical characteristic test, it could be drawn that the increasing propylene glycol concentration increased clarity, pH, and gel viscosity. Increasing propylene glycol concentration also decreased dissolution-%, decreased DE-%, increased lag time and decreased diffusion coefficient. The physical characteristic test and the caffeine releasing test were analyzed by using the one-way ANOVA with 95% and probability ( $p=0,05$ ) level SPSS.*

*Based on the results of the research, it could be concluded that the different propylene glycol concentration as humectant, affects significantly to the physical characteristics, such as the pH and viscosity tests, and to the caffeine releasing in gel, such as the dissolution-%, DE-%, lag time, and diffusion coefficient.*

**Keywords :** *Caffeine, gel, propylene glycol, lag time, dissolution*

## INTRODUCTION

Cellulite is topographical skin alteration that happen in 85% post-adolescent women (Hexsel *et al.*, 2006). It is normally occurred on the skin thighs, belly, and buttocks of whom that have an adrenergic receptor (Djajadisastra, 2008). Topical anticellulite is used to reducing cellulite. Caffeine is used as active ingredient

that based on stimulation beta adrenergic receptor mechanism.

Hydrophillic gel are suitable to be used as cosmetic base because of its cooling effect, good appearance, and not sticky. Carbomer have also be chosen as gel-base because it can form a thicked gel (Allen, 2002) and produce a stable product (Amnuakit, 200). Gel component are usually consisted of humectant, a substance that can control water evaporation change between the product and the air, in the container or in the

skin (Rukminingsih, 2009). Propylene glycol is commonly used as humectant that has mechanism in repairing irregular epidermis appearance of the skin cellulite condition. Propylene glycol can increase a solubility of many substances, one of which is caffeine (Rowe *et al.*, 2009) and it can influence a swelling and viscoelasticity of carbomer (Islam *et al.*, 2004). Propylene glycol is also known as a substance that influence release rate of active substances (Amnuakit *et al.*, 2005).

## METHODS

Object of this research was a physical characteristic and release rate of caffeine in gel as humectant in different concentration of 10%, 20%, and 30%. The parameter used to determine caffeine release rate was the value of lag time and coefficient diffusion based on Higuchi's Equation.

Free variable in this research was propylene glycol concentration of 10%, 20%, and 30%. Bound variable in this research were physical characteristics and release rate of caffeine. Physical characteristic gel consisted of organoleptic, value of pH, and viscosity. The value of lag time and diffusion coefficient could perform the rate of its caffeine's release.

The instruments used were mortar and stamper, glass tools, porcelain cup, *Hot Plate stirrer* model L-81 (Labinco), *Tablet Dissolution Apparatus VDA-6DR USP Standards* (VEEGO), pH 210 *Microprocessor* pH meter (HANNA), *spektrofotometer UV mini 1240 UV-Visible* (Shimadzu), *viscosimeter Rion VT-04*, and *paddle over disk*.

The materials used to form a caffeine gel, physical characteristic test and release rate were anhydrous caffeine, carbomer, propylene glycol, TEA, nipagin, KH<sub>2</sub>PO<sub>4</sub>, NaOH, cellophane membran, buffer pH 7 and buffer pH 4.

The method of this research was dissolving a caffeine into mixture of propylene glycol and water with magnetic stirrer until it dissolved well then added to carbomer gel base which was swelled and added enough water. Each formula consisted of a different propylene glycol concentration (table I).

Each formula has been tested its physical characteristic, of organoleptic, pH, and viscosity, and been done a release test of caffeine in gel using cellophane membrane and paddle over disk. The 2 grams of preparation gel were put into paddle over disk which cellophane membrane equipped, then put it into the dissolution vessel contained of 900 ml of phosphate buffer pH 7,4 at 37°C, and was stirred at 50 rpm speeds. The sample was taken a 10,0 ml of it, at 5', 10', 15', 30', 45', 60', 90', 120', 150', 180', 240', 300', and 360' minutes stirring time. The absorbance of caffeine was viewed at the maximum wavelength of 273 nm on the 7,4 pH phosphate buffer blanko. The result datas were analyzed by using One way ANOVA for the normal distribution, and Kruskal Wallis for the abnormal distribution data.

## RESULTS AND DISCUSSION

Based on the result on this research, it could be concluded that the increased propylene

**Table I. The Calculation of component Caffeine Gel Preparation**

Substances	Calculation	F1 (g)	FII (g)	FIII (g)	FIV (g)
Caffeine	3% x 150 g	4,5	4,5	4,5	4,5
Carbomer	0,5% x 150 g	0,75	0,75	0,75	0,75
TEA	0,5% x 150 g	0,75	0,75	0,75	0,75
Propylene- Glycol	10% x 150 g	15	-	-	-
	20% x 150 g	-	30	-	-
	30% x 150 g	-	-	45	-
Nipagin	0,2% x 150 g	0,3	0,3	0,3	0,3
Aqua destilata	Up to 150 g	Up to 150	Up to 150	Up to 150	Up to 150

glycol concentration can increase clarity, pH's value, viscosity caffeine gel. Propylene glycol can increase caffeine solubility in gel and tend to be more alkalized, than carbomer that makes the carbomer swelling more easily, so that the gel clarity and pH were also increased. Carbomer swelling process causes increasing in the polymer cross-linked so then the viscosity is also

Formula I showed a highest value of dissolution-% among other formulas, because amount of adding propylene glycol was just 10% and consisted more water than of formula II and formula III, so caffeine were more easily solubilized into the dissolution medium. The different water amount in each formula actually didn't give a significant effect on the caffeine gel


**Table II. Result of Physical Characteristic and Caffeine Release Rate Test**

Determine	Formula				
	F I	F II	F III	F IV	F V
Organoleptic:					
• Form	Gel Clear	Gel Clear	Gel Clear (the most clear)	Gel Turbid	Gel Green and clear
• Colour					
• Odour	-	-	-	-	Tea's aromatic
Taste	Cool	Cool	Cool	Cool	Cool
pH	5,57 ± 0,03	5,75 ± 0,02	6,04 ± 0,02	5,20 ± 0,04	6,31 ± 0,02
Viscosity (P)	171,67 ± 2,58	182,50 ± 2,74	200 ± 0,00	158,33 ± 2,58	38,33 ± 5,16
Lag time (menit)	9,9987 ± 0,1092	16,8348 ± 0,5452	21,8593 ± 0,5473	7,2659 ± 0,2131	42,2219 ± 0,4138
Diffusion coefficient (10 <sup>-7</sup> x cm <sup>2</sup> /minutes)	9,6967 ± 0,1470	5,7465 ± 0,1831	4,3986 ± 0,1093	13,2191 ± 0,3799	2,2763 ± 0,234
% Dissolution	44,4888 ± 2,1111	35,3835 ± 1,3010	31,2257 ± 2,2495	54,8373 ± 3,7105	3,7876 ± 0,2986
% DE (Dissolution Efficiency)	56,2986 ± 3,7196	54,2677 ± 1,8589	51,5982 ± 2,1647	58,1339 ± 3,1156	52,7523 ± 1,8602

increased. The result of the organoleptic test were shown at table II.

Caffeine release test was used to know the total caffeine solubilized and caffeine release rate. Caffeine release test was used negative control, that was a preparation gel without adding propylene glycol and the positive control, that was anti cellulite preparation that available in the market. Based on the result data, the relation between solubilized caffeine with in certain time interval, and the total solubilized caffeine of each formula (picture 1).

preparation's release, if it was compared to the formula IV as negative control that showed the highest amount release because at the most of it preparation contained water, and without be added with propylene glycol. The negative control showed a highest release amount, because it did not contain an inhibitor of releasing factor such as propylene glycol. Formula V as positive control is showed a lowest result. It was because the preparation was formulated for slow release and consisted of other active anticellulite beside caffeine. Based on statistical test showed that increased propylene glycol concentration of 10% did not make any

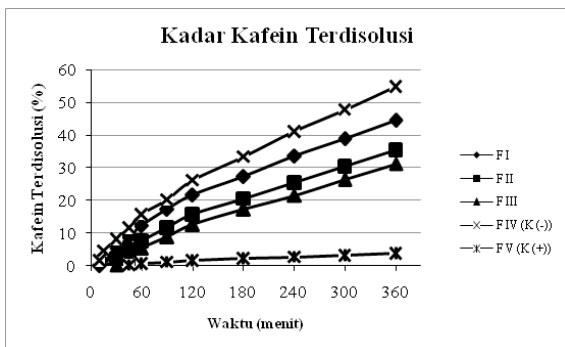

Picture 1. Caffeine dissolution content

significant difference reduction of dissolution-%.

Having in mind the levels of dissolution, then it was calculated the levels of Dissolution Efficiency (DE) that states the ratio between the area under the curve in the time  $t$  and the rectangular area that limits the 100% ordinate and absciss. Area under the curve or AUC describes the levels of drug content in time as a measure of size and total of the bioavailability of drug. DE is usually used to determine the ability or efficiency of the drug is dissolved in the media until a certain time. Increased concentrations of 10% propylenglycol in the formula however did not cause a decrease in DE-% value significantly. While 20% increased propylenglycol concentration in the formula caused a decrease in DE-% value significantly.

The release rate of caffeine in gel were counted by applying the Higuchi equation. Caffeine release rate could be seen from the value of lag time and the value of diffusion coefficient. Release rate of active substance in gel were influenced by physical gel characteristic that was gel viscosity. Increasing gel viscosity was caused by density of polymer cross-linked forms. Increasing the cross-linked polymer density caused a gel hydrophobisity and inhibiting release rate of active substance (Sinko, 2006 : 519). A hydrophobisity also causes steric hydrance effect hydro so that inhibiting hydroxyl group

interaction with its medium, that inhibits caffeine release rate.

Based on the result it concluded that, increasing propylene glycol leads to the increasing of lag time value and decrease the diffusion coefficient. The increased lag time value showed an inhibiting caffeine release rate from the gel basis up to the limit between its base and membrane surface. Based on the statistical test of lag time and diffusion coefficient, each formula tested with various concentration of propylene glycol showed significant differences.

Caffeine gel preparation as anticellulite worked locally and didn't enter systemic circulation. Adding propylene glycol as humectant in gel preparation are expected to improve skin appearance in cellulite condition and to restrain caffeine release rate in order to keep it work locally and doesn't enter the systemic circulation.

## CONCLUSION

Based on the result of this research, can be concluded that :

1. Increased propylene glycol concentration gives significant effect to increase clarity, pH value, and viscosity value of caffeine gel preparation.
2. Increased 10% of propylene glycol concentration in the formula doesn't give significant effect of caffeine dissolution-% and DE-%.
3. Lag time value is increased and diffusion coefficient value is decreased, as result of increasing propylene glycol concentration.
4. The best formula is Formula III. It has the most clear physical characteristic, the longest release rate, and the less caffeine content, and best function as humectant.

## REFERENCE

Allen, L.V. 2002. *The Art, Science and Technology of Pharmaceutical*

- Compounding*. 2<sup>nd</sup> Ed. Washington DC : American Pharmacists Association.
- Amnuakit, T., Ikeuchi, I., Ogawara, K., Higaki, K., dan Himura, T. 2005. Skin Permeation of Propranolol from Polymeric Film Containing Terpene Enhancers for Transdermal Use, *Int J. Pharm* 289(1-2) : 167.
- Amnuakit, T., Ingkatawornwong, S., Maneenuan, D., dan Worachotekamjorn, K. 2008. Caffeine Topical Gel Formulation, *IJPS* 4 (1) : 16-24.
- Djajadisastra, J. 2008. *Effect of cream, gel and Ointment dosage forms on in-vitro skin penetration of caffeine using franz diffusion cell*. UI repository. <http://repository.ui.ac.id/contents/koleksi/11/5a7469fb52aa316e1cffb9c5f18201e8204cb148.pdf> (28 Agustus 2010).
- Hexsel, D., Zechmeister do Prado, D., Rao, J dan Goldman, M.P. 2006. Topical Management of Cellulite. In Goldman, M.P., Bacci, P.A., Leibaschoff, G., Hexsel, D., and Angelini, F (Eds). *Cellulite Pathophysiology and Treatment*. New York : Taylor and Francis Group.
- Islam, M.T., Rodry'guez-Hornedo, N., Ciotti, S dan Ackerman, C. 2004. Rheological Characterization of Topical Carbomer Gels Neutralized to Different pH, *AAPS* 21 : 7.
- Rowe, R.C., Sheskey, P.J dan Quinn, M. E. 2009. *Handbook of Pharmaceutical Excipient*. 6<sup>th</sup> Ed. Washington DC : Pharmaceutical Press and American Pharmacists Association.
- Rukminingsih, F. 2009. Studi in vitro Pengaruh Gliserol, Propilenglikol, dan Sorbitol terhadap Pelepasan Perak Sulfadiazin dari Krim Setomakrogol. *Proceeding Seminar Nasional Farmasi "Antioksidan dalam Sediaan Obat, Kosmetika, Makanan dan Minuman"*. STIFAR "YAYASAN PHARMASI" Semarang : 309-316.
- Sinko, P. J. 2006. *Martin's Physical Pharmacy and Pharmaceutical Science*. 5<sup>th</sup> Ed. Philadelphia : Lippincott Williams & Wilkins.

